




Landcruising Verve 25 (Release 2011)

Our Verve slackline webbing is the red coloured counterpart to our classic White Magic. The Verve offers a superior combination of low strain, high-strength, low weight and durability. The dynamic behaviour is even more defined and perfected compared to White Magic. The true red color (no surface coating) and the soft touch finishing the new accents.

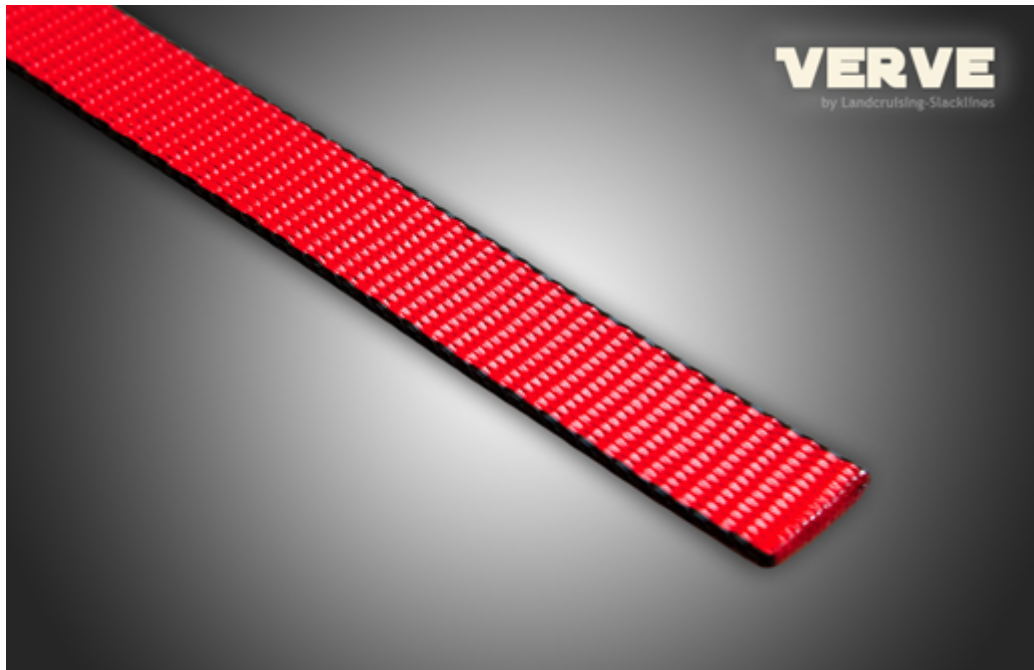

The Landcruising Verve is characterized by the following details:

- flat webbing 25 mm (1 inch) width made of Polyester fibers
- average break strength >33 kN (3,3 t) - [please see graph](#)
- min. 3sigma break strength 30 kN (3 t)
- 7 % elongation at 10 kN
- 58 gram weight by the meter
- high-quality and durable color
- soft touch and bounce, very good elasticity
- excellent for surfing at 20-30 m length and beautiful longline behaviour
- no labels or prints for pure aesthetics
- if used as longline - be aware of the maximum permissible pretension of 10 kN!
- made in Germany

Parametertabelle: geprüft auf Zwick 1485 - Dossier Nr. 162793

Prüfgegenstand	:	Dehnung	: 6-8%
Artikelnummer	:	min.Bruchlast	: 30000 N
Breite	: 025	Material	: PES
Farbe	:	Charge	:
Farbtext	: rot	WE-Nr.	:
Prüfer	:	Vorkraft	: 200 N
Gurtdicke	: 2,0 - 3,0 mm	Dehnungswert bei	: 10000 N
Gurtbreite	: 23,5 - 25,5 mm	Prüfgeschwindigkeit:	100 mm/min

Ergebnisse:

Nr	Fmax N	ϵ -F max %	Dehn.b. 10000 N %	Dicke a mm	Breite b mm	Metergewicht g	Schuß/10cm
max	40000		8,00				
min	30000		6,00				
1	33115	20,39	7,03	2,45	24,55	58,10	59
2	33328	20,59	6,90	2,45	24,55	58,10	59
3	33216	20,18	7,04	2,45	24,55	58,10	59

Statistik:

Serie n = 3	Fmax N	ϵ -F max %	Dehn.b. 10000 N %	Dicke a mm	Breite b mm	Metergewicht g	Schuß/10cm
\bar{x}	33220	20,38	6,99	2,45	24,55	58,10	59
s	106	0,20	0,08	0,000	0,00	0,00	0
v	0,32	1,00	1,16	0,00	0,00	0,00	0,00

Parametertabelle:

Prüfgegenstand	:		Dehnung	:	6-8%
Artikelnummer	:		min.Bruchlast	:	30000 N
Breite	:	025	Material	:	PES
Farbe	:		Charge	:	
Farbtext	:	rot	WE-Nr.	:	
Prüfer	:		Vorkraft	:	200 N
Gurtdicke	:	2,0 - 3,0 mm	Dehnungswert bei	:	10000 N
Gurtbreite	:	23,5 - 25,5 mm	Prüfgeschwindigkeit:	:	100 mm/min

Seriengrafik: